

# Effect of Machining Parameters on Tool Wear and Hole Quality of AISI 316L Stainless Steel in Conventional Drilling

*By Ahmad Zubair Sultan*

14

2nd International Materials, Industrial, and Manufacturing Engineering Conference, MIMEC2015,  
4-6 February 2015, Bali Indonesia

10

## Effect of Machining Parameters on Tool Wear and Hole Quality of AISI 316L Stainless Steel in Conventional Drilling

A. Z. Sultan<sup>a</sup>, Safian Sharif<sup>b,\*</sup>, Denni Kurniawan<sup>b</sup>

<sup>a</sup>Politeknik Negeri Ujung Pandang, Tamalanrea, Makasar 90245, Indonesia

<sup>b</sup>Faculty of Mechanical Engineering, Universiti Teknologi Malaysia, Skudai, Johor 81300, Malaysia

### Abstract

This paper focuses on the effect of machining parameters on tool wear and hole quality in terms of diameter error, roundness, cylindricity, and surface roughness. In this work, the drilling was conducted using uncoated carbide tool with diameter of  $4 \pm 0.01$  mm with point angle of  $135^\circ$  and helix angle of  $30^\circ$ . The drilling was done at different levels of spindle speed (18 and 30 mm<sup>min</sup>-1) and feed rate (0.03, 0.045 and 0.06 mm<sup>rev</sup>-1). Austenitic stainless steel AISI 316L was the workpiece material. Comparatives analysis was done on hole diameter, roundness, cylindricity, and surface roughness of the drilled holes by experimentation. From the result, the hole quality characteristics are mostly influenced by cutting speed and feed rate. An exception was for circularity error where two tail t-test for circularity error indicates that cutting speed and feed rate give no significant influence on circularity error. As the cutting speed increases, the surface roughness decreases (1.09  $\mu$ m). Contrary, when the feed rate increases, the surface roughness value increases as well. For cylindricity error, lower cutting speed and lower feed rate will give better result. In terms of diameter error, feed rate influences more than cutting speed. Minimum diameter error was achieved when low cutting speed and low feed rate were employed.

© 2015 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Selection and Peer-review under responsibility of the Scientific Committee of MIMEC2015

**Keywords:** Surface roughness; Roundness; Cylindricity; Drilling Austenitic Stainless Steel

### 1. Introduction

Although metal cutting methods have improved in the manufacturing industry, conventional drilling process still remains one of the most common processes. Drilling can be applied to various workpiece materials. The surface

\* Corresponding author

E-mail address: [safian@fkm.utm.my](mailto:safian@fkm.utm.my)

quality is important for the functional behavior of the mechanical parts [1]. The most obvious factors influencing accuracy of drilled holes are cutting speed and feed rate [18]. Cutting speed and feed rate significantly affect the surface roughness of the machined surface whereby high cutting speed and low feed rate resulted in the better surface finish [3]. In material removal processes, an improper selection of cutting conditions will result in rough surfaces and dimensional errors. Therefore, it is necessary to understand the relationship among the various controllable parameters and to identify the important parameters that influence the quality of drilling.

Austenitic stainless steel especially AISI 316L is used widely in aeronautical, biomedical, and food industries. However, the poor machinability makes it a typical difficult-to-cut material, often resulting low hole quality when drilling process is conducted on this material. They bond very strongly to the tool, and chips often remain stuck to the tool after cutting [4]. These properties were responsible for the rapid wear on the cutting tool hence resulting in short tool life and rapid tool failure [4]. Researches regarding the machinability of the austenitic stainless steels have highlighted the insufficiency of the data for establishing of the optimum cutting conditions. Considering this, this study investigates the machinability of austenitic stainless steel AISI 316L during conventional drilling process using uncoated carbide tools, by varying the cutting parameters of cutting speed and feed rate.

## 2. Experimental

### 2.1 Material.

In this study, AISI 316L austenitic stainless steel was used as the workpiece material. This steel are generally used in the production of exhaust manifolds, furnace parts, heat exchangers, jet engine parts, pharmaceutical and photographic equipment, valve and pump trim, chemical/pharmaceuticals equipment, digesters, tanks, evaporators, pulp, paper and textile processing equipment, food preparation equipment particularly in chloride environments, medical implants (including pins, screws, and orthopedic implants like total hip and knee replacements). The chemical composition of the workpiece materials was determined with EDS (Energy Dispersive Spectroscopy) analysis and given in Table 1.

Table 1. Chemical compositions of 316L austenitic stainless steel

Fe	Cr	N	Ni	Mo	Mn	Si	S	C	P
Bal	16.5	0.1	10.23	2.6	2.0	0.6	0.03	0.03	0.03

Samples with dimension of 102 x 60 x 10 mm<sup>3</sup> and hardness of 179.4 HV was used in the drilling trials. The samples were prepared using milling and surface grinding in order to meet above dimension and to prepare surface references for both drilling trials and measurement process. The samples were clamped on precision jig.

### 2.2 Drilling experiments.

Drilling tests were performed on DECKEL HO DMC835V CNC machining center using uncoated carbide drill bits with diameter of 4 ± 0.01 mm, point angle of 135°, and helix angle of 30°. Previous study recommended the cutting tool to have point angle between 118° and 135° and helix angle of 24° to 32° [5], hence the selected tool geometry. To guarantee consistency of each test, a new drill tool was used for each trial. Holes were drilled at each trial until average flank wear on the tool reached 0.3 mm. The experiments were performed at two cutting speeds (18 and 30 mm/min) and three feed rates (0.03, 0.045 and 0.06 mm/rev) while the hole depth was kept constant at 10 mm. Tool overhang was set at 30 mm. All drilling experiments were conducted under 18.3 l/min flood drilling with 6% commercial FUCHS Ecocod 68CF2 as cutting fluid. Surface roughness (Ra) was measured by an Accretech Handysurf surface profilometer. The cut-off and sampling lengths for each measurement were taken as 0.8 and 4 mm, respectively. For each hole, the surface roughness was measured parallel to the drilled axis at four radial positions at 0°, 90°, 180° and 270° using the surface profilometer. The surface roughness was an average taken from twelve measurements from three repetitions on each position.

In these experiments, the final shape of the hole was determined using Renishaw cyclone coordinate measurement machine (CMM). 19 diameters of the holes were calculated using the standard built-in software package of the CMM. Twenty points were probed to determine the diameter in the horizontal plane, and the diameter of each hole was checked at 0.5 mm (i.e., near the top of the produced hole), 5.5 mm (i.e., near the middle of the produced hole), and 9.5 mm (i.e., near the bottom of the produced hole) along the hole axis height. All diameters were checked thoroughly. The difference between the measured diameter and the drill diameter was the diameter error. After drilling each hole, wear was measured at  $d/6$  mm located at chisel edge [6] by a Raxvision microscope at 40X magnification.

Cylindricity is a tolerance of form that checks cylindrical features only. All circular and longitudinal elements on the surface of the cylinder must lie within two concentric cylinders separated by the value of cylindricity tolerance which is measured on radius. Circularity is a tolerance of form and measured from a cross-section perpendicular to the axis of a hole or a cylinder to ensure that all elements are within a two concentric circle tolerance zones. Twenty points were probed for each hole cross-section, and the circularity was calculated using the built-in software package of the CMM. The circularity of each hole was also checked at three different heights along the hole axis.

### 3. Results and analysis

#### 3.1. Effect of drilling parameters on tool wear.

Tool wear is an important issue since wear on drill affects the hole quality and tool life of the drill. As shown in Fig. 1, the feed rate was found to be more significant compare to cutting speed, impacting the tool life, due to the large feed rate, material must be scratch at each revolution will also be greater. Lower feed rate and cutting speed results in higher tool life.

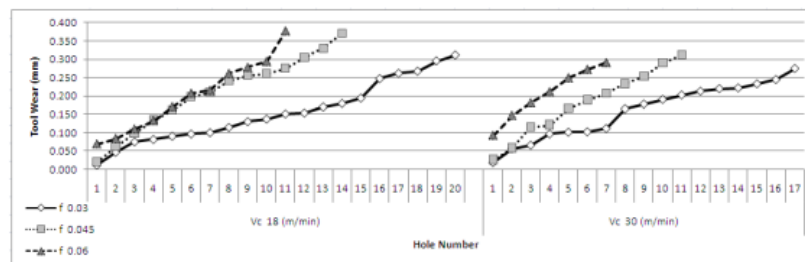


Fig.1. Average flank wear progress at different cutting speed and feed rate

With the tool life criterion that the average flank wear reached 0.3 mm, the number of holes that can be drilled at cutting speed of 18 m/min is 20 holes, 14 holes, and 11 holes at a feed rate of 0.03, 0.045, and 0.06 mm/rev, respectively. In conditions of higher cutting speed is 30 m/min, the number of holes that can be drilled before tool wear of 0.3 mm was 17, 11, and 7 holes at the same level of feed rate, i.e. 0.03, 0.045, and 0.06 mm/rev, respectively. Higher feed rate will cause the material volume that must be removed also higher in the same revolution.

During drilling, flank wear observed increase rapidly in all cutting speeds and feed rate applied. Drill experienced similar modes of failure during the experiment trial. These were non uniform flank wear, chipping, and catastrophic failure. Chipping of the cutting edges was common at most cutting speeds, perhaps due to the immediate loss of sharp cutting edge. Attrition wear was observed to be the prominent wear mechanism operating at all cutting speeds and feed rates. At the same time, the ability of the AISI 316L to retain its strength at elevated temperature during drilling also contributes to the resulting wear pattern of the drill.

Another contributing factor to the brittle failure of the cutting edge could be due to the low modulus of AISI 316L which can cause vibration and chatter during drilling. Chipping was the dominant mode of failure at most

cutting speeds. However, close observation of the worn drills showed that under the same cutting speed, tool with lower feed rate suffered less damage when compared to the higher feed rate tool.

### 3.2. Effect of drilling parameters on diameter error.

Generally, as the cutting speed increases, the diameter of the hole drilled errors also increase (Fig. 2). This is because as the spindle rotation speed is higher, the vibration caused by the spindle also gets higher. In addition, the worsening hole profile was caused by multiple changes of direction during drill bit movement along the hole axis.

Diameter error showed a tendency to decrease in the next drill holes. This is because the tool wear rate increase so although the spindle vibrates the same as the previous hole, but due to the existing wear, the diameter irregularities do not occur too large to exceed the previous diameter. Minimum diameter error (7.417  $\mu\text{m}$ ) was achieved when the lowest cutting speed (18 m/min) and lowest feed rate (0.03 mm/rev) were applied.

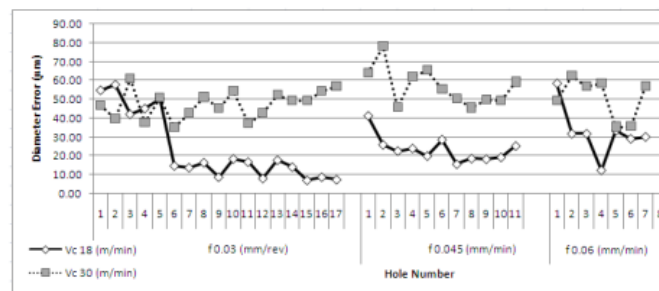


Fig. 2. Variation in diameter error for different cutting speed and feed rate.

### 3.3. Effect of drilling parameters on circularity.

For drilled holes, circularity or roundness is another important quality characteristic. Based on feed rate groups, the variation in average circularity error for different holes is given in Fig. 3. No clear trend was apparent; however there was a slight increase in circularity error values with an increase in cutting speed. A t-test for circularity error gives  $s_{\text{tat}} = 0.143 < c_{\text{critical}} = 2.228$  for different cutting speed and  $s_{\text{tat}} = 0.593 < c_{\text{critical}} = 2.228$  for different feed rate. Based on the t-test result, null hypothesis accepted where no significant difference between the two cutting speeds and two feed rates applied on circularity error.

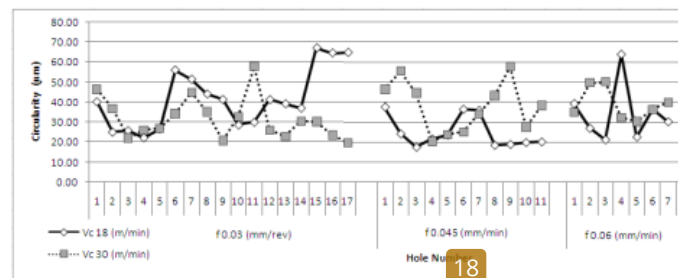


Fig. 3. Variation in circularity error for different cutting speed and feed rate.

### 3.4. Effect of drilling parameters on cylindricity.

Fig. 4 shows error of cylindricity at different level of feed rate and cutting speed. In terms of cylindricity error, it can be seen that lower cutting speed (18 m/min) and lower feed rate (0.03 mm/rev) will give better result (0.035 mm). This can be mainly attributed to that the lower cutting speed leads to a minimal vibration in drilling, thus lower cylindricity error was obtained. While lower feed rate means the drill bit moving slowly with lower material removal rate along hole axis. As a result, hole axis tends to be consistent in constant position.

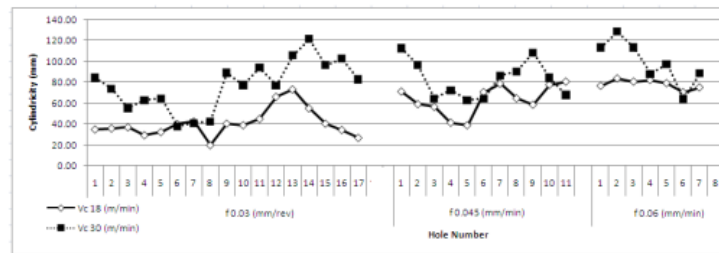


Fig. 4. Variation in cylindricity error for different cutting speed and feed rate.

23

### 3.5. Effect of drilling parameters on surface roughness.

16

Cutting speed has a significant influence on the surface roughness produced. When cutting speed increases, the surface roughness values of the holes produced decrease (from 1.34  $\mu\text{m}$  to 1.09  $\mu\text{m}$ ). The decrease in surface roughness with increasing cutting speed can be explained by decreasing built up edge (BUE) formation tendency. Due to the highly ductile structure of austenitic stainless steels, they have tendency to form a large and unstable BUE. The presence of the large and unstable BUE causes poor surface finish. The trend lines in Fig. 5 shown that when number of holes drilled is increased, the surface roughness values gradually increase due to the increase of the tool wear.

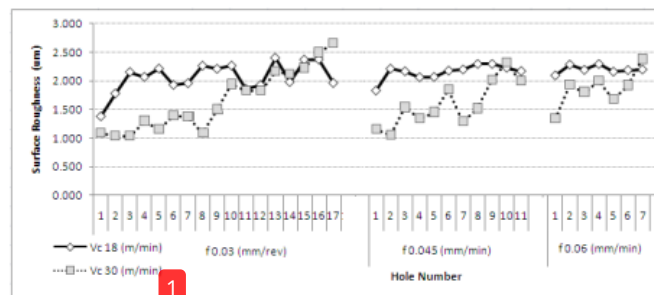


Fig. 5. Variation in surface roughness for different cutting speed and feed rate.

## 4. Concluding remarks

1

In drilling AISI 316L stainless steel using uncoated carbide tool with diameter of  $4 \pm 0.01$  mm with point angle of  $135^\circ$  and helix angle of  $30^\circ$  at middle speed of 18 and 30  $\text{mmin}^{-1}$  and feed rate of 0.03, 0.045, and 0.06  $\text{mmrev}^{-1}$ , diameter error, cylindricity, and surface roughness are mostly influenced by the cutting speed and feed rate. The feed rate and cutting speed give no significant influence on value of the circularity error. As the cutting speed increases, the surface roughness decreases. In contrary when the feed rate increases, surface roughness value increases as well. At the same time, tool wear influences surface roughness. For cylindricity error, lower cutting speed and lower feed rate will give better result. In terms of diameter error, feed rate influenced more than cutting speed. During drilling austenitic stainless steel, drill experienced similar modes of failure at all cutting speeds and feed rates employed, i.e. non uniform flank wear, chipping, and catastrophic failure.

## Acknowledgements

Financial supports from the Ministry of Education, Malaysia and Universiti Teknologi Malaysia through Research University Grant (No. 05H27) and Fundamental Research Grant Scheme (No. 4F285) are gratefully acknowledged.

## References

- [1]. Benardos, P.G. and G.C. Vosniakos, Predicting surface roughness in machining: a review. *International Journal of Machine Tools and Manufacture*, 2003. 43(8): p. 833-844.
- [2]. Islam, M.N., N.H. Rafi, and P. Charoon. An Investigation into Effect of Canned Cycles on Drilled Hole Quality. in *Proceedings of the World Congress on Engineering 2009 Vol I*. 2009. London, U.K.
- [3]. Sharif, S., E.A. Rahim, and H. Sasahara, Machinability of Titanium Alloys in Drilling, in *Towards Achieving Enhanced Properties for Diversified Applications*, D.A.K.M.N. Amin, Editor. 2012.
- [4]. Trent, E.M. and P.K. Wright., *Metal cutting* 4th ed, ed. . 2000, Woburn, MA: Butterworth–Heinemann Ltd.
- [5]. Todd, R.H. and D.K. Allen, *Manufacturing Processes Reference Guide*. 1994, Industrial Press Inc. p. 512.
- [6]. Çaydaş, U., et al., Performance evaluation of different twist drills in dry drilling of AISI 304 austenitic stainless steel. *Materials and Manufacturing Processes*, 2011. 26(8): p. 951-960.

# Effect of Machining Parameters on Tool Wear and Hole Quality of AISI 316L Stainless Steel in Conventional Drilling

ORIGINALITY REPORT

23%

SIMILARITY INDEX

## PRIMARY SOURCES

- 1 M. Anthony Xavier, M. Adithan. "Determining the influence of cutting fluids on tool wear and surface roughness during turning of AISI 304 austenitic stainless steel", *Journal of Materials Processing Technology*, 2009  
51 words — 2%  
Crossref
- 2 Sumon Kundu, Bikash Choudhuri, Ruma Sen. "CNC Machinability study of AISI 316L & Optimization of Machining parameters using TLBO algorithm", *Materials Today: Proceedings*, 2022  
45 words — 2%  
Crossref
- 3 Zul Fahmi Omar, Denni Kurniawan. "Effect of water treatment on AISI 316L stainless steel biocorrosion resistance", *AIP Publishing*, 2020  
38 words — 1%  
Crossref
- 4 [www.issr-journals.org](http://www.issr-journals.org)  
Internet  
36 words — 1%
- 5 [www.ijert.org](http://www.ijert.org)  
Internet  
28 words — 1%
- 6 Ghany, K.A.. "Cutting of 1.2mm thick austenitic stainless steel sheet using pulsed and CW Nd:YAG laser", *Journal of Materials Processing Tech.*, 20051015  
26 words — 1%  
Crossref
- 7 Bhardwaj, B., R. Kumar, and P. K. Singh. "Effect of machining parameters on surface roughness in  
24 words — 1%



end milling of AISI 1019 steel", Proceedings of the Institution of Mechanical Engineers Part B Journal of Engineering Manufacture, 2014.

Crossref

- 
- 8 S. Sharma. "Optimization of Machining Process Parameters for Surface Roughness of Al-Composites", Journal of The Institution of Engineers (India): Series C, 2013 21 words — 1%  
Crossref
- 
- 9 [www.arnjournals.org](http://www.arnjournals.org) 18 words — 1%  
Internet
- 
- 10 [www.iosrjournals.org](http://www.iosrjournals.org) 18 words — 1%  
Internet
- 
- 11 Dudzinski, D.. "A review of developments towards dry and high speed machining of Inconel 718 alloy", International Journal of Machine Tools and Manufacture, 200403 16 words — 1%  
Crossref
- 
- 12 Kaynak, Yusuf. "Matkap Ile Delik Delme Esnasinda Kesme Parametrelerinin Kesme Kuvveti ve Sicakligin Degisimine Etkisinin Deneysel Olarak Incelenmesi", Marmara Universitesi (Turkey) 16 words — 1%  
ProQuest
- 
- 13 Ming Chen. "OPTIMIZATION STUDIES ON HOLE-MAKING TOOLS FOR HIGH-PERFORMANCE CUTTING AUSTENITIC STAINLESS STEEL", Machining Science and Technology, 4/2007 16 words — 1%  
Crossref
- 
- 14 LISAURA WALKIRIA RODRIGUEZ ALVARADO, PEDRO TAMAYO MEZA, USIEL SANDINO SILVA RIVERA. "COMPORTAMIENTO DINÁMICO Y ANÁLISIS DE ESCENARIOS DEL SISTEMA DE PRODUCCIÓN EN UNA LÍNEA DE 15 words — 1%

---

15 Ali Erçetin, Kubilay Aslantas, Özgür Özgün. "Micro-end milling of biomedical Tz54 magnesium alloy produced through powder metallurgy", *Machining Science and Technology*, 2020 14 words — 1%

Crossref

---

16 Xiaobin Cui, Jun Zhao, Chao Jia, Yonghui Zhou. "Surface roughness and chip formation in high-speed face milling AISI H13 steel", *The International Journal of Advanced Manufacturing Technology*, 2011 13 words — 1%

Crossref

---

17 [isomase.org](http://isomase.org) 12 words — < 1%

Internet

---

18 [scholarsmine.mst.edu](http://scholarsmine.mst.edu) 12 words — < 1%

Internet

---

19 Ali, Salah H.R., and Omar M. Mohamd. "Dimensional and Geometrical Form Accuracy of Circular Pockets Manufactured for Aluminum, Copper and Steel Materials on CNC Milling Machine Using CMM", *International Journal of Engineering Research in Africa*, 2015. 11 words — < 1%

Crossref

---

20 Tauseef Aized, Muhammad Amjad. "Quality improvement of deep-hole drilling process of AISI D2", *The International Journal of Advanced Manufacturing Technology*, 2013 11 words — < 1%

Crossref

---

21 Tsao, C.C.. "Evaluation of thrust force and surface roughness in drilling composite material using Taguchi analysis and neural network", *Journal of Materials Processing Tech.*, 20080718 11 words — < 1%

Crossref

---

- 22 Capus, J.. "Machined PM parts: does the 'X-Factor' hold key to success?", Metal Powder Report, 200412  
Crossref 10 words — < 1%
- 
- 23 Gao, Yuan, Xin Huang, Ming Jie Lin, Zheng Guo Wang, and Rong Lei Sun. "Analysis and Prediction of Surface Integrity in Machining: A Review", Applied Mechanics and Materials, 2014.  
Crossref 10 words — < 1%
- 
- 24 V.N. Gaitonde. "Multiperformance Optimization in Turning of Free-Machining Steel Using Taguchi Method and Utility Concept", Journal of Materials Engineering and Performance, 04/2009  
Crossref 9 words — < 1%
- 
- 25 Wang, Yang Jun, M. Zhou, and Y.H. Zhao. "The Study on Three-Dimensional Roughness of Machined Surface in High Speed Milling of SiCp/Al Composites", Advanced Materials Research, 2011.  
Crossref 9 words — < 1%
- 
- 26 [link.springer.com](http://link.springer.com)  
Internet 9 words — < 1%
- 
- 27 "Optimisation of surface roughness with GA approach in turning 15% SiC<SUB align=right>p reinforced AlSi7Mg2 MMC material", International Journal of Machining and Machinability of Materials, 2006  
Crossref 8 words — < 1%
- 
- 28 Arici, Anil . "Development of Al-Si-Mg Alloys for Permanent Mold Casting and High-Pressure Vacuum Die Casting Applications.", Universite du Quebec a Chicoutimi (Canada), 2019  
ProQuest 8 words — < 1%
- 
- 29 Coldwell, H.. "Rapid machining of hardened AISI H13 and D2 moulds, dies and press tools", 8 words — < 1%

30 Gokkaya, H.. "The effects of cutting tool geometry and processing parameters on the surface roughness of AISI 1030 steel", *Materials and Design*, 2007

8 words — < 1%

Crossref

31 Gu, J.. "Tool life and wear mechanism of uncoated and coated milling inserts", *Wear*, 199904

8 words — < 1%

Crossref

32 Ohgo, K.. "A study of the peeling of the built-up edge from a cutting tool during the discontinuous machining of a carbon steel and its effect on tool life", *Wear*, 197803

8 words — < 1%

Crossref

33 [compmech.unipv.it](http://compmech.unipv.it)

Internet

8 words — < 1%

34 L. Francis Xavier, Paramasivam Suresh. "Drilling studies on the prepared aluminum metal matrix composite from wet grinder stone dust particles", *Science and Engineering of Composite Materials*, 2018

7 words — < 1%

Crossref

35 *Multidiscipline Modeling in Materials and Structures*, Volume 9, Issue 3 (2013-10-19)

7 words — < 1%

Publications

36 Ribeiro-Carvalho Sílvia, C.H. Lauro, Horovistiz Ana, J.P. Davim. "Development of FEM-based digital twins for machining difficult-to-cut materials: A roadmap for sustainability", *Journal of Manufacturing Processes*, 2022

6 words — < 1%

Crossref

---

EXCLUDE QUOTES OFF

EXCLUDE SOURCES OFF

EXCLUDE BIBLIOGRAPHY ON

EXCLUDE MATCHES OFF



ScienceDirect®

Journals & Books



## Procedia Manufacturing

*Open access*

Articles & Issues ▾


 Search in this journal

# 2nd International Materials, Industrial, and Manufacturing Engineering Conference, MIMEC2015, 4-6 February 2015, Bali, Indonesia

Edited by Denni Kurniawan, Fethma M. Nor

Volume 2,

Pages 1-578 (2015)

 [Download full issue](#)



[Submit Your Paper](#)

[View Articles](#)

[Guide for Authors](#)

[Abstracting/ Indexing](#)

#### Journal Metrics

> CiteScore: **1.39**

Source Normalized Impact per Paper (SNIP): **0.855**

SCImago Journal Rank (SJR): **0.313**

#### Your Research Data

> [Share your research data](#)

> [MethodsX co-submission](#)

#### Related Links

> [Author Stats](#)

> [Researcher Academy](#)

> [Author Services](#)

> [Try out personalized alert features](#)

### You did the work, now get the CRediT

A fairer, more transparent way  
of showcasing author contributions

[READ MORE](#)



**CRediT**

# Procedia Manufacturing - Editorial Board

## Editor-in-Chief

**Professor A. Shih**

University of Michigan, Ann Arbor, Michigan, USA

## Editorial Board

**Dr. J. Cao**

Northwestern University, Evanston, Illinois, USA

**Professor S.J. Hu**

University of Michigan, Ann Arbor, Michigan, USA

**Professor S. Kara**

UNSW Australia, Sydney, New South Wales, Australia

**Prof. Dr.-Ing. G. Lanza**

Karlsruhe Institute of Technology (KIT), Karlsruhe, Germany

**Dr. J. Ni**

University of Michigan, Ann Arbor, Michigan, USA

**Professor R. Shivpuri**

The Ohio State University, Columbus, Ohio, USA

## Procedia Manufacturing

### Readers

[View Articles](#)

[Volume/ Issue Alert](#)

[Personalized Recommendations](#)

[User Rights](#)

### Authors

[Guide for Authors](#)

[Submit Your Paper](#)

[Early Career Resources](#)

[Rights and Permissions](#)

[Support Center](#)

### Librarians

[Abstracting/ Indexing](#)

### Editors

[Publishing Ethics Resource Kit](#)

↓ [Guest Editor Guide](#)

↓ [Guest Editor Checklist](#)

↓ [FTP Guide](#)

[Manuscript Tracking Form](#)



2nd International Materials, Industrial, and Manufacturing Engineering Conference, MIMEC2015,  
4-6 February 2015, Bali Indonesia

## Effect of Machining Parameters on Tool Wear and Hole Quality of AISI 316L Stainless Steel in Conventional Drilling

A. Z. Sultan<sup>a</sup>, Safian Sharif<sup>b,\*</sup>, Denni Kurniawan<sup>b</sup>

<sup>a</sup>Politeknik Negeri Ujung Pandang, Tamalanrea, Makasar 90245, Indonesia

<sup>b</sup>Faculty of Mechanical Engineering, Universiti Teknologi Malaysia, Skudai, Johor 81300, Malaysia

---

### Abstract

This paper focuses on the effect of drilling parameters on tool wear and hole quality in terms of diameter error, roundness, cylindricity, and surface roughness. In this work, the drilling was conducted using uncoated carbide tool with diameter of  $4 \pm 0.01$  mm with point angle of  $135^\circ$  and helix angle of  $30^\circ$ . The drilling was done at different levels of spindle speed (18 and 30  $\text{mm}^{-1}$ ) and feed rate (0.03, 0.045 and 0.06  $\text{mm}^{-1}$ ). Austenitic stainless steel AISI 316L was the workpiece material. Comparatives analysis was done on hole diameter, roundness, cylindricity, and surface roughness of the drilled holes by experimentation. From the result, the hole quality characteristics are mostly influenced by cutting speed and feed rate. An exception was for circularity error where a two tail t-test for circularity error indicates that cutting speed and feed rate give no significant influence on circularity error. As the cutting speed increases, the surface roughness decreases ( $1.09 \mu\text{m}$ ). Contrary, when the feed rate increases, the surface roughness value increases as well. For cylindricity error, lower cutting speed and lower feed rate will give better result. In terms of diameter error, feed rate influences more than cutting speed. Minimum diameter error was achieved when low cutting speed and low feed rate were employed.

© 2015 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Selection and Peer-review under responsibility of the Scientific Committee of MIMEC2015

*Keywords:* Surface roughness; Roundness; Cylindricity; Drilling Austenitic Stainless Steel

---

### 1. Introduction

Although metal cutting methods have improved in the manufacturing industry, conventional drilling process still remains one of the most common processes. Drilling can be applied to various workpiece materials. The surface

\* Corresponding author

E-mail address: [safian@fkm.utm.my](mailto:safian@fkm.utm.my)



quality is important for the functional behavior of the mechanical parts [1]. The most obvious factors influencing the accuracy of drilled holes are cutting speed and feed rate [2]. Cutting speed and feed rate significantly affect the surface roughness of the machined surface whereby high cutting speed and low feed rate resulted in the better surface finish [3]. In material removal processes, an improper selection of cutting conditions will result in rough surfaces and dimensional errors. Therefore, it is necessary to understand the relationship among the various controllable parameters and to identify the important parameters that influence the quality of drilling.

Austenitic stainless steel especially AISI 316L is used widely in aeronautical, biomedical, and food industries. However, the poor machinability makes it a typical difficult-to-cut material, often resulting low hole quality when drilling process is conducted on this material. They bond very strongly to the tool, and chips often remain stuck to the tool after cutting [4]. These properties were responsible for the rapid wear on the cutting tool hence resulting in short tool life and rapid tool failure [4]. Researches regarding the machinability of the austenitic stainless steels have highlighted the insufficiency of the data for establishing of the optimum cutting conditions. Considering this, this study investigates the machinability of austenitic stainless steel AISI 316L during conventional drilling process using uncoated carbide tools, by varying the cutting parameters of cutting speed and feed rate.

## 2. Experimental

### 2.1 Material.

In this study, AISI 316L austenitic stainless steel was used as the workpiece material. This steel are generally used in the production of exhaust manifolds, furnace parts, heat exchangers, jet engine parts, pharmaceutical and photographic equipment, valve and pump trim, chemical/pharmaceuticals equipment, digesters, tanks, evaporators, pulp, paper and textile processing equipment, food preparation equipment particularly in chloride environments, and medical implants (including pins, screws, and orthopedic implants like total hip and knee replacements). The chemical composition of the workpiece materials was determined with EDS (Energy Dispersive Spectroscopy) analysis and given in Table 1.

Table 1. Chemical compositions of 316L austenitic stainless steel

Fe	Cr	N	Ni	Mo	Mn	Si	S	C	P
Bal	16.5	0.1	10.23	2.6	2.0	0.6	0.03	0.03	0.03

Samples with dimension of 102 x 60 x 10 mm<sup>3</sup> and hardness of 179.4 HV was used in the drilling trials. The samples were prepared using milling and surface grinding in order to meet above dimension and to prepare surface references for both drilling trials and measurement process. The samples were clamped on precision jig.

### 2.2 Drilling experiments.

Drilling tests were performed on DECKEL MAHO DMC835V CNC machining center using uncoated carbide drill bits with diameter of  $4 \pm 0.01$  mm, point angle of 135°, and helix angle of 30°. Previous study recommended the cutting tool to have point angle between 118° and 135° and helix angle of 24° to 32° [5], hence the selected tool geometry. To guarantee the consistency of each test, a new drill tool was used for each trial. Holes were drilled at each trial until average flank wear on the tool reached 0.3 mm. The experiments were performed at two cutting speeds (18 and 30 mm/min) and three feed rates (0.03, 0.045 and 0.06 mm/rev) while the hole depth was kept constant at 10 mm. Tool overhang was set at 30 mm. All drilling experiments were conducted under 18.3 l/min flood drilling with 6% commercial FUCHS Ecocool 68CF2 as cutting fluid. Surface roughness (Ra) was measured by an Accretech Handysurf surface profilometer. The cut-off and sampling lengths for each measurement were taken as 0.8 and 4 mm, respectively. For each hole, the surface roughness was measured parallel to the drilled axis at four radial positions at 0°, 90°, 180° and 270° using the surface profilometer. The surface roughness was an average taken from twelve measurements from three repetitions on each position.

In these experiments, the final shape of the hole was determined using Renishaw cyclone coordinate measurement machine (CMM). The diameters of the holes were calculated using the standard built-in software package of the CMM. Twenty points were probed to determine the diameter in the horizontal plane, and the diameter of each hole was checked at 0.5 mm (i.e., near the top of the produced hole), 5.5 mm (i.e., near the middle of the produced hole), and 9.5 mm (i.e., near the bottom of the produced hole) along the hole axis height. All diameters were checked thoroughly. The difference between the measured diameter and the drill diameter was the diameter error. After drilling each hole, wear was measured at  $d/6$  mm located at chisel edge [6] by a Raxvision microscope at 40X magnification.

Cylindricity is a tolerance of form that checks cylindrical features only. All circular and longitudinal elements on the surface of the cylinder must lie within two concentric cylinders separated by the value of the cylindricity tolerance which is measured on radius. Circularity is a tolerance of form and measured from a cross-section perpendicular to the axis of a hole or a cylinder to ensure that all elements are within a two concentric circle tolerance zones. Twenty points were probed for each hole cross-section, and the circularity was calculated using the built-in software package of the CMM. The circularity of each hole was also checked at three different heights along the hole axis.

### 3. Results and analysis

#### 3.1. Effect of drilling parameters on tool wear.

Tool wear is an important issue since wear on drill affects the hole quality and tool life of the drill. As shown in Fig. 1, the feed rate was found to be more significant compare to cutting speed, impacting the tool life, due to the large feed rate, material must be scratch at each revolution will also be greater. Lower feed rate and cutting speed results in higher tool life.

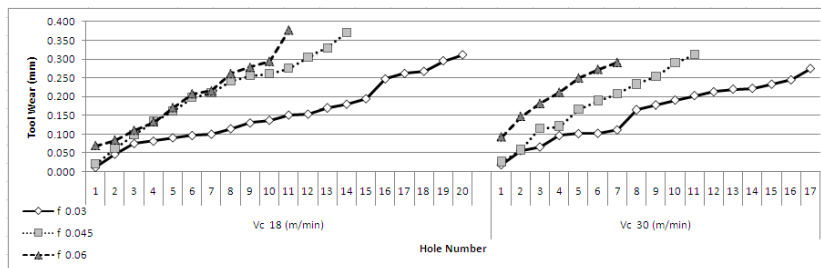


Fig.1. Average flank wear progress at different cutting speed and feed rate

With the tool life criterion that the average flank wear reached 0.3 mm, the number of holes that can be drilled at cutting speed of 18 m/min is 20 holes, 14 holes, and 11 holes at a feed rate of 0.03, 0.045, and 0.06 mm/rev, respectively. In conditions of higher cutting speed is 30 m/min, the number of holes that can be drilled before tool wear of 0.3 mm was 17, 11, and 7 holes at the same level of feed rate, i.e. 0.03, 0.045, and 0.06 mm/rev, respectively. Higher feed rate will cause the material volume that must be removed also higher in the same revolution.

During drilling, flank wear observed increase rapidly in all cutting speeds and feed rate applied. Drill experienced similar modes of failure during the experiment trial. These were non uniform flank wear, chipping, and catastrophic failure. Chipping of the cutting edges was common at most cutting speeds, perhaps due to the immediate loss of sharp cutting edge. Attrition wear was observed to be the prominent wear mechanism operating at all cutting speeds and feed rates. At the same time, the ability of the AISI 316L to retain its strength at elevated temperature during drilling also contributes to the resulting wear pattern of the drill.

Another contributing factor to the brittle failure of the cutting edge could be due to the low modulus of AISI 316L which can cause vibration and chatter during drilling. Chipping was the dominant mode of failure at most

cutting speeds. However, close observation of the worn drills showed that under the same cutting speed, tool with lower feed rate suffered less damage when compared to the higher feed rate tool.

### 3.2. Effect of drilling parameters on diameter error.

Generally, as the cutting speed increases, the diameter of the hole drilled errors also increase (Fig. 2). This is because as the spindle rotation speed is higher, the vibration caused by the spindle also gets higher. In addition, the worsening hole profile was caused by multiple changes of direction during drill bit movement along the hole axis.

Diameter error showed a tendency to decrease in the next drill holes. This is because the tool wear rate increase so although the spindle vibrates the same as the previous hole, but due to the existing wear, the diameter irregularities do not occur too large to exceed the previous diameter. Minimum diameter error (7.417  $\mu\text{m}$ ) was achieved when the lowest cutting speed (18 m/min) and lowest feed rate (0.03 mm/rev) were applied.

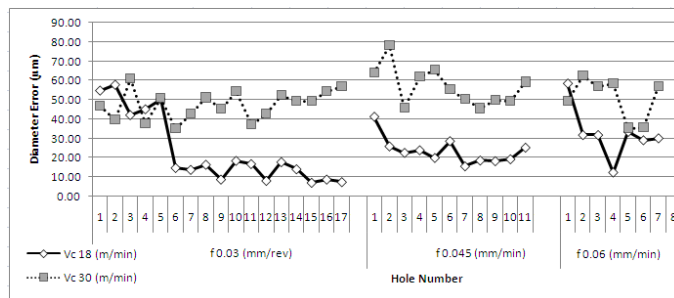


Fig. 2. Variation in diameter error for different cutting speed and feed rate.

### 3.3. Effect of drilling parameters on circularity.

For drilled holes, circularity or roundness is another important quality characteristic. Based on feed rate groups, the variation in average circularity error for different holes is given in Fig. 3. No clear trend was apparent; however there was a slight increase in circularity error values with an increase in cutting speed. A t-test for circularity error gives  $s_{\text{tat}} = 0.143 < c_{\text{critical}} = 2.228$  for different cutting speed and  $s_{\text{tat}} = 0.593 < c_{\text{critical}} = 2.228$  for different feed rate. Based on the t-test result, null hypothesis accepted where no significant difference between the two cutting speeds and two feed rates applied on circularity error.

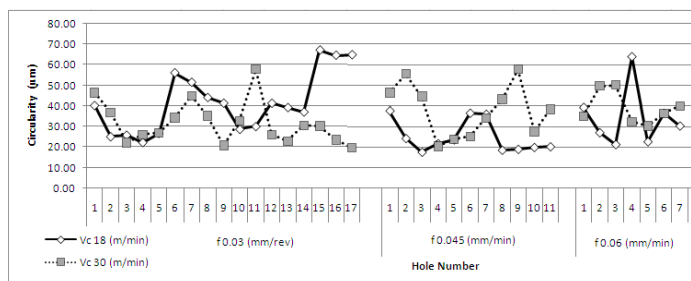


Fig. 3. Variation in circularity error for different cutting speed and feed rate.

### 3.4. Effect of drilling parameters on cylindricity.

Fig. 4 shows error of cylindricity at different level of feed rate and cutting speed. In terms of cylindricity error, it can be seen that lower cutting speed (18 m/min) and lower feed rate (0.03 mm/rev) will give better result (0.035 mm). This can be mainly attributed to that the lower cutting speed leads to a minimal vibration in drilling, thus lower cylindricity error was obtained. While lower feed rate means the drill bit moving slowly with lower material removal rate along hole axis. As a result, hole axis tends to be consistent in constant position.

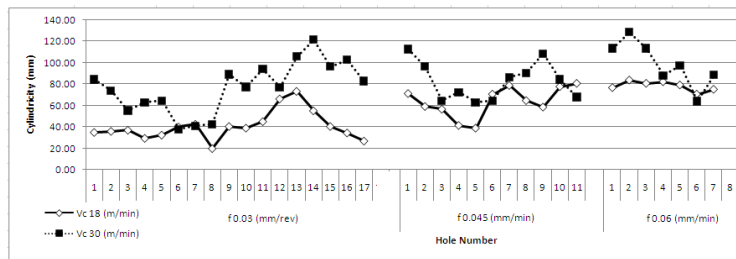


Fig. 4. Variation in cylindricity error for different cutting speed and feed rate.

### 3.5. Effect of drilling parameters on surface roughness.

Cutting speed has a significant influence on the surface roughness produced. When cutting speed increases, the surface roughness values of the holes produced decrease (from  $1.34 \mu\text{m}$  to  $1.09 \mu\text{m}$ ). The decrease in surface roughness with increasing cutting speed can be explained by decreasing built up edge (BUE) formation tendency. Due to the highly ductile structure of austenitic stainless steels, they have tendency to form a large and unstable BUE. The presence of the large and unstable BUE causes poor surface finish. The trend lines in Fig. 5 shown that when number of holes drilled is increased, the surface roughness values gradually increase due to the increase of the tool wear.

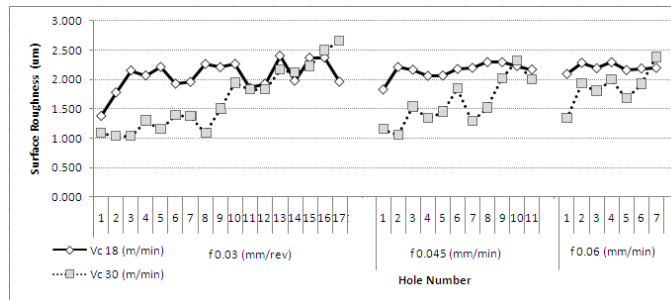


Fig. 5. Variation in surface roughness for different cutting speed and feed rate.

## 4. Concluding remarks

In drilling AISI 316L stainless steel using uncoated carbide tool with diameter of  $4 \pm 0.01 \text{ mm}$  with point angle of  $135^\circ$  and helix angle of  $30^\circ$  at spindle speed of 18 and 30  $\text{mmin}^{-1}$  and feed rate of 0.03, 0.045, and 0.06  $\text{mmrev}^{-1}$ , diameter error, cylindricity, and surface roughness are mostly influenced by the cutting speed and feed rate. The feed rate and cutting speed give no significant influence on value of the circularity error. As the cutting speed increases, the surface roughness decreases. In contrary when the feed rate increases, surface roughness value increases as well. At the same time, tool wear influences surface roughness. For cylindricity error, lower cutting speed and lower feed rate will give better result. In terms of diameter error, feed rate influenced more than cutting speed. During drilling austenitic stainless steel, drill experienced similar modes of failure at all cutting speeds and feed rates employed, i.e. non uniform flank wear, chipping, and catastrophic failure.

## Acknowledgements

Financial supports from the Ministry of Education, Malaysia and Universiti Teknologi Malaysia through Research University Grant (No. 05H27) and Fundamental Research Grant Scheme (No. 4F285) are gratefully acknowledged.

## References

- [1]. Benardos, P.G. and G.C. Vosniakos, Predicting surface roughness in machining: a review. *International Journal of Machine Tools and Manufacture*, 2003. 43(8): p. 833-844.
- [2]. Islam, M.N., N.H. Rafi, and P. Charoon. An Investigation into Effect of Canned Cycles on Drilled Hole Quality. in *Proceedings of the World Congress on Engineering 2009 Vol I*. 2009. London, U.K.
- [3]. Sharif, S., E.A. Rahim, and H. Sasahara, Machinability of Titanium Alloys in Drilling, in *Towards Achieving Enhanced Properties for Diversified Applications*, D.A.K.M.N. Amin, Editor. 2012.
- [4]. Trent, E.M. and P.K. Wright., *Metal cutting* 4th ed, ed. . 2000, Woburn, MA: Butterworth–Heinemann Ltd.
- [5]. Todd, R.H. and D.K. Allen, *Manufacturing Processes Reference Guide*. 1994, Industrial Press Inc. p. 512.
- [6]. Çaydaş, U., et al., Performance evaluation of different twist drills in dry drilling of AISI 304 austenitic stainless steel. *Materials and Manufacturing Processes*, 2011. 26(8): p. 951-960.


• Abstract ID130 and ID131 Yahoo/Sent ☆

• Bair Sultan <bair\_sultan@yahoo.co.nz> To: info@mimec.me Tue, 6 Jan 2015 at 9:38 am ☆


Dear MIMEC2015  
Abstract ID130 and ID131 are attached  
Thank you and best wishes

[Sent from Yahoo Mail on Android](#)

[Download all attachments as a zip file](#)



MIMEC2015... .doc 29kB



MIMEC2015... .doc 29.5kB

### Effect of Machining Parameters on Tool Wear and Hole Quality of AISI 316L During Conventional Drilling

Ahmad Zubair Sultan<sup>1</sup>, Safian Sharif, D. Kurniawan<sup>2</sup>  
<sup>1</sup>Department of Mechanical Engineering, Politeknik Negeri Ujung Pandang, Makassar, Indonesia  
<sup>2</sup>Department of Manufacturing and Industrial Engineering, Faculty of Mechanical Engineering, Universiti Teknologi Malaysia, Skudai, Johor, Malaysia  
[\\*bair\\_sultan@yahoo.co.nz](mailto:bair_sultan@yahoo.co.nz)

#### Abstract

This paper focused on the effect of drilling parameter on tool wear and hole quality such as diameter error, roundness, cylindricity and surface roughness. In this work, drilling conducting using uncoated carbide tool diameter  $4 \pm 0.01$  mm with point angle  $135^\circ$  and helix angle  $30^\circ$ . In order to find the best drilling parameter for austenitic stainless steel AISI 316L as workpiece material, conventional drilling experiment conducted with commercial mineral oil Fuchs Ecocool 68CF2 as cutting fluid with flow rate 13.8l/min were performed at different levels of spindle speed (18 and 30  $\text{mm}^{-1}$ ) and feed rate (0.03, 0.045 and 0.06  $\text{mm rev}^{-1}$ ). The experimental are conducted using DECKEL MAHO-DMC 825V machining center and results were collected using Raxvision microscope, KN810 Renishaw CMM and Accretach handysurf portable surface roughness tester. Comparatives analysis has been done between hole diameter, roundness, cylindricity and surface roughness of drilled holes by experimentation. From the result, all of the hole quality characteristics are mostly influenced by cutting speed and feed rate except for circularity error. Two tail t-test for circularity error gives  $t_{stat} = 0.143 < t_{table} = 2.228$  for different cutting speed and  $t_{stat} = 0.593 < t_{table} = 2.228$  for different feed rate so cutting speed and feed rate gives not significant influence on value

On Thursday, 23 April 2015 4:22 PM, Denni Kurniawan <denni@utm.my> wrote:

Dear student researchers,

Please reformat your papers for MIMEC2015 to Procedia Manufacturing format.  
Email me the MS word file by this Saturday 25 April.

Thank you and best wishes,  
Denni

2 Attachments • Scanned by Gmail [Info Icon]

