

# Minimum quantity of lubricant drilling of stainless steel using refined palm olein: effect of coating tools on surface roughness and tool wear

*By Ahmad Zubair Sultan*



## Minimum quantity of lubricant drilling of stainless steel using refined palm olein: Effect of coating tool on surface roughness and tool wear

Ahmad Zubair Sultan<sup>a</sup>, Safian Sharif<sup>b,\*</sup>, Fethma M. Nor<sup>c</sup>, Denni Kurniawan<sup>d,†</sup>

<sup>a</sup>Department of Mechanical Engineering, Politeknik Negeri Ujung Pandang, Makassar 90245, Indonesia

<sup>b</sup>School of Mechanical Engineering, Universiti Teknologi Malaysia, Johor Bahru 81310, Malaysia

<sup>c</sup>Department of Mechanical Engineering, Curtin University, Miri 98009, Malaysia

<sup>d</sup>Faculty of Engineering, Universiti Teknologi Brunei, Gadong BE1410, Brunei Darussalam

### Abstract

65

This study investigates the effect of cutting tool coating during minimum quantity of lubricant (MQL) drilling of austenitic stainless steel using refined palm olein (RPO) as lubricant/cutting fluid. Two types of tool coating, TiAlN and TiSiN, on tungsten carbide drill with diameter  $4 \pm 0.01$  mm, point angle of  $130^\circ$  and helix angle of  $30^\circ$  were used in this study to machine AISI 316L stainless steel workpiece with hardness of 179.5 HV. Drilling tests were conducted with cutting speed of 12 m/min and feed rate of 0.025 mm/rev. Tool overhang was set at 30 mm. The MQL system in this trial was with 5.5 bar of air, the spray output was 27 ml/h, adjusted  $20^\circ$  and located 35 mm away from the cutting tool. Tool wear was measured during experiment using tool microscope connected to image analyser. Surface roughness (Ra) was measured with cut-off and sampling lengths of 0.8 mm and 4 mm, respectively. For each hole, the surface roughness was measured parallel to the drilled axis at four radial positions at  $0^\circ$ ,  $90^\circ$ ,  $180^\circ$  and  $270^\circ$ , repeated three times repeated for each position. Tool life of the drill and surface roughness of the drilled hole were the machining responses investigated. It was found that the MQL-RPO drilling using TiSiN coated carbide tool produced better result in terms of tool life (reaching 7.54 minutes) compared to using TiAlN coated tool (of only 4.19 minutes). Related to surface roughness, the best result was obtained by TiAlN coated tool. Through two-factor analysis of variance (ANOVA) with replication on first hole, it was found that the wear of the tool affects the surface roughness significantly while different types of coating has no significant effect on tool wear and surface roughness. In addition, there is no interaction between types of coating and wear of the tool that influence the surface roughness.

© 2019 The Authors. Published by Elsevier Ltd.

This is an open access article under the CC BY-NC-ND license (<https://creativecommons.org/licenses/by-nc-nd/4.0/>)

Selection and peer-review under responsibility of the scientific committee of the 14th Global Congress on Manufacturing and Management (GCMM-2018).

\* Corresponding author.

E-mail address: safian@utm.my

† Corresponding author.

E-mail address: denni.kurniawan@utb.edu.bn

2351-1016 © 2019 The Authors. Published by Elsevier Ltd.

This is an open access article under the CC BY-NC-ND license (<https://creativecommons.org/licenses/by-nc-nd/4.0/>)

Selection and peer-review under responsibility of the scientific committee of the 14th Global Congress on Manufacturing and Management (GCMM-2018).

10.1016/j.promfg.2019.02.059

Keywords: Machinability; stainless steel; minimum quantity of lubricant; drilling; coated carbide; tool wear; surface roughness.

## 1. Introduction

Negative effects of cutting fluids on manufacturing cost, human health, and environment have raised alarming signal to the machining industries [1-2]. As a response, reducing cutting fluids is suggested whenever possible. With increasing awareness of health and environmental conditions, vegetable oils have become alternative lubricants for industrial applications. It is also supported by the properties of the vegetable oils that have good lubrication and kinematic viscosity as well as them being non-toxic, made from renewable resources, and biodegradable [3]. Various trials carried out on machining, stainless steel in particular, in order to evaluate vegetable oil based cutting fluids such as rapeseed oil [4], coconut oil [5], sunflower oil and canola oil [6], palm oil [7] and castor oil [8].

Some of the alternatives which are under investigation are using vegetable oil based-minimum quantity lubricant (MQL-VO). The introduction of MQL-VO has been shown to work well in short-term tests over a range of processes. MQL is beneficial in terms of tool life in turning [9], deep-hole drilling [10], surface roughness [11], lower process costs and produced dry chips [12]. It was shown that MQL can be regarded as an alternative to flood cutting from the viewpoints of tool performance, cost, health, safety and environment [13] and MQL can improve plant conditions, conserve ecology environment, reduce producing cost and improve producing quality [14]. However, in terms of diameter error, testing indicates that there is no difference, between MQL and the flooded system, and regarding to circularity error and cylindricity error, in average MQL has the worst performance compared to dry and flooded cooling [15]. It is likely that long-term capability and robustness of MQL technique remain still unanswered and more material specific issues may require additional testing [2].

Belluco and De Chiffre [4] conducted flooded drilling 316L using high speed steel (HSS)-coated and found that average tool life ranging from 23 to 63 minutes with mixtures of mineral oil, rapeseed oil-ester oil, rapeseed oil-ester meadow foam oil, and vegetable oil-rape seed oil-ester oil. Using tool wear and cutting forces as performance criteria, vegetable oil-based cutting fluids outperformed the mineral oil based. Tool life was increased by 177% while thrust force was reduced by 7%. The presence of sulphur and phosphorus-based additives in the vegetable oil-based fluids helped prevent adhesion. In another research, Belluco and De Chiffre [8] tested vegetable oil based metal working fluid through different operations. HSS-E tool was used to make holes on 316L workpiece. They did performance evaluation of vegetable and mineral cutting fluids by measuring the cutting force and they reported that vegetable cutting fluid outperformed the commercial mineral cutting fluid.

During drilling AISI 304, Kuram et al. [8] applied vegetable oil based metal working fluids formulated of crude sunflower (CS) and refined sunflower oil (RS), comparing them with commercial mineral cutting fluid (CM) as control. Three types of metal working fluids i.e.: mixture of CS1+ 20% Tween85 (viscosity of 1.7 cp), mixture of S1+ 20% Tween20 (viscosity of 1.9 cp) and mixture of S2 + 20% Tween20 + 15% Tween85 (viscosity of 1.3 cp). Based on the experiment result, the lowest roughness value of 1.01  $\mu\text{m}$  and highest of 2.26  $\mu\text{m}$  were achieved using RS2 and CM, respectively. Compared to RS1, RS2 gave better roughness value for all machining conditions, which might be related to difference in viscosity. Viscosity affects the flow of cutting fluid. Cutting fluid with low viscosity expectedly can reach the tool-workpiece interface more effectively, making chips to be flushed away from the cutting zone and preventing a finished drilled hole surface from becoming scratched [16].

Ozcelik et al., [17] compared two different refined sunflower oil (RS) when drilling AISI 304 stainless steel. Metal working fluid formulated using mixture of: RS1 + 20% Tween85 (viscosity of 1.5 cp) and RS2 + 20% Tween85 + 9% Peg400 (viscosity of 1.1 cp). Mineral metal working fluid (MO) and semi synthetic cutting fluid (SS) were used as reference [17]. Related to surface roughness, minimum value of 1.36  $\mu\text{m}$  were obtained by using RS1 mixture, followed by RS2 mixture with 1.43  $\mu\text{m}$ , MO with 1.48  $\mu\text{m}$ , and being maximum at 1.92  $\mu\text{m}$  by SS. RS1 produced

better surface roughness compared to RS2 although the former has higher viscosity. This can be attributed to the lubrication ability, in which cutting fluid with low viscosity has poor lubricating capability [16]. This result hinted that there is a critical cutting fluid viscosity value that can give the best surface roughness out of this AISI 304 stainless steel workpiece. In another research, Ozcelik et al. [18] explored the influence of vegetable-based cutting fluids on the HSS-E wear when drilling AISI 304 stainless steel. The vegetable-based metal working fluids were crude sunflower refined sunflower oil, and canola oil. Experimental results show that due to its higher lubricant properties, refined canola oil-based cutting fluid gave better performance compared to the others.

Related to research on difficult-to-machine materials such as austenitic stainless steel, there are not many studies have been conducted. Further research is required on cooling conditions, tool materials, cutting parameters and tool geometries [19] in order to explore the productivity of this material machining. The properties of austenitic stainless steel have unfavourable impact on the machining process, with the result that machining of austenitic stainless steel is considered difficult due its unfavourable properties when subjected to machining. Because of the low heat conductivity of austenitic stainless steel, generated heat cannot be transferred into the workpiece and chips effectively. As a result, heat concentration at the tool cutting edge occurs [19]. In machining, these characteristics cause the formation of built-up edges when carbide tools are used, giving rapid tool failure and poor tool life [20, 21]. At the same time, it is necessary to meet the surface integrity requirements, where tool wear can lead to residual stresses and poor surface roughness in the drilled hole surface [22].

Palm oil is one of commonly used vegetable oils. In making the palm oil, after crude palm oil refining, the oil may be separated by thermo mechanical means (involving cooling, crystallization, and filtering) into liquid (refined palm olein) and solid phases (palm stearin). This study investigates the machinability of austenitic stainless steel AISI 316L under drill with Refined Palm Olein based Minimum Quantity Lubricant (MQL-RPO) technique using carbide tools. with TiAlN and TiSiN coated carbide tools are used in this study.

## 2. Methodology

Austenitic stainless steel AISI 316L was used as the workpiece materials in the present study. The dimension of the workpiece material was 102 mm x 60 mm x 10 mm with microhardness of 179.5 HV. Specimen was prepared using milling and surface grinding to meet above dimension and to prepare surface references for both drilling trials and measurement process. The specimen was clamped on precision jig before through hole drilling on the specimen.

The workpiece material is known as one of the difficult-to-machine materials and is mainly used in the production of pharmaceutical and photographic equipment, chemical/ pharmaceuticals equipment, paper and textile processing equipment, food preparation equipment particularly in chloride environments and medical implants such as pins, screws and orthopaedic implants like total hip and knee replacements. The chemical compositions of workpiece materials were determined with EDS (Energy Dispersive Spectroscopy) analysis (Table 1).

Table 1. Chemical compositions of 316L austenitic stainless steel (in % volume).

Fe	Cr	N	Ni	Mo	Mn	Si	S	C	P
Balance	16.5	0.1	10.23	2.6	2.0	0.6	0.03	0.03	0.03

Drilling tests were conducted on DECKEL MAHO DMC835V CNC machining centre with cutting speed of 12 m/min and feed rate of 0.025 mm/rev using coated carbide drill bits with diameter of  $4 \pm 0.01$  mm, point angle of  $130^\circ$  and helix angle of  $30^\circ$ . The drill bits were TiAlN and TiSiN coated carbide tools. Refined palm olein (RPO) was used as minimum quantity lubricant (MQL) fluids with the characteristics given in Table 2. The MQL system in this trial was delivered using Economizer I system which are completely self-contained. Positive displacement, continuous spray systems were used. With 5.5 bar air supplied, the spray output was 27 ml/h, adjusted  $20^\circ$  and located 35 mm away from the cutting tool. A new drill tool was used in each trial to ensure the same initial conditions of each test. Tool wear was measured continuously during experimental process using Raxvision microscope connected to iSolution image analyser software. Tool wear was measured at  $d/6$  mm located to chisel edge [23] after particular drilling intervals. Tool overhang was set at 30 mm. Surface roughness (Ra) was measured with an Accret Handysurf portable surface roughness tester. The cut-off and sampling lengths for each measurement taken were 0.8 and 4 mm, respectively. For each hole, the surface roughness was measured parallel to the drilled axis at four radial positions at

0°, 90°, 180° and 270° using the surface roughness tester. The surface roughness value was an average taken from twelve measurements from three times repeat at each position.

Table 2. Properties of the MQL fluid.

MQL Fluids	RPO	Test Method
Appearance	Yellow	Visual
Density at 15°C (kg/L)	0.91	ASTM D1298-85(90)
Viscosity at 40°C (mm <sup>2</sup> /s)	53.18	ASTM D445-94
Viscosity at 100°C (mm <sup>2</sup> /s)	10.36	ASTM D445-94
Viscosity index	188	ASTM D2270-93
Pour point (°C)	6	ASTM D97-93
Flash point (°C)	320	ASTM D92-90

29

### 3. Results and Discussion

#### 3.1. Experimental results

Tool wear and surface roughness obtained under MQL-RPO drilling using different tool coating are presented in Fig. 1. New tool represented first hole while worn out tool represented finish hole where tool reached tool life criteria.

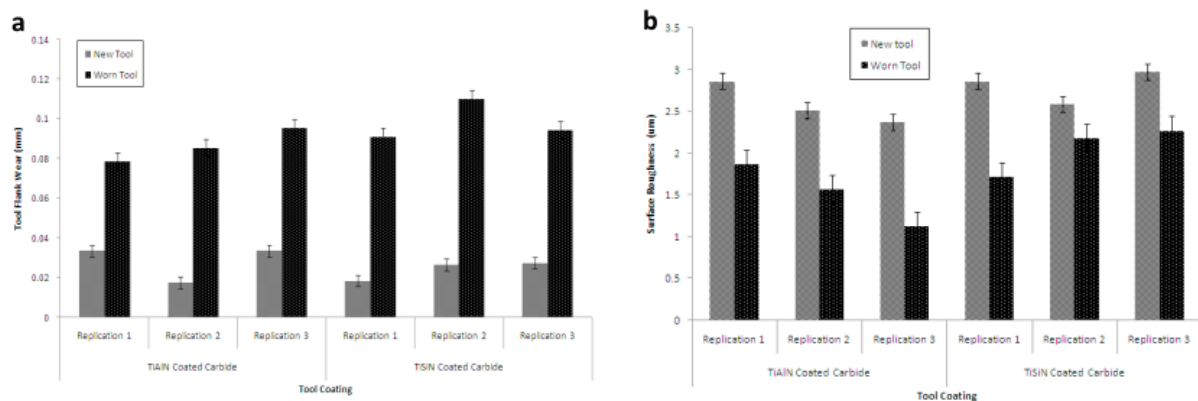


Fig. 1. (a) Tool wear and (b) surface roughness under MQL-RPO drilling.

#### 3.2. Statistical analysis

Analysis made by using a two-factor analysis of variance (ANOVA) with replication to determine whether there is a significant effect of different tool coating and different tool conditions simultaneously on tool wear response [24]. The null hypothesis (H0) is no tool wear difference among all trials while alternative hypothesis (H1) stated that differences occur among all trials. ANOVA test result for tool wear is presented in Table 3.

Table 3. ANOVA result for tool wear data.

Source of variation	Sum of square	Degree of freedom	Mean square	F	P-value	F critic	
Tool coating	0.00005	1	0.00005	0.67	0.44	5.32	Not significant
Tool condition	0.01320	1	0.01320	185.32	< 0.01	5.32	Significant
Interaction	0.00019	1	0.00019	2.70	0.14	5.32	Not significant
Within	0.00057	8	0.00007				
Total	0.01401	11					

Related to tool coating, since  $F(0.67) < F_{critical}(5.32)$ ,  $H_0$  prevails this means that different tool coating has no significant effect on tool wear. Interaction between coolant condition and tool coating did not exist and did not influence the tool wear, since  $F(2.70) < F_{critical}(5.32)$  where  $H_0$  is accepted.

Flank wear progression with the increase in the number of drilled holes under MQL-RPO drilling is shown in Fig. 2. Obviously during MQL-RPO drilling, the tool life of the TiSiN coated tool were found to be higher than that of TiAlN coated tools. Similar result was reported by Wang et al. during high speed milling of hardened steel material [25]. These were mainly due to superiority of the hardness and oxidation temperature of the TiSiN coating. TiAlN coated drill bit wore more rapidly and was only able to drill ten holes before tool failure, or approximately 55 % compared to the tool life of TiSiN coated tool. The tool failure modes included flank wear, micro chipping and flaking. Similar pattern was obvious at initial wear stage for both tools where tool wear increases rapidly until the third hole. During stable wear stages of the tool, flank wear increased almost linearly. Both tools failed before reaching the maximum tool wear.

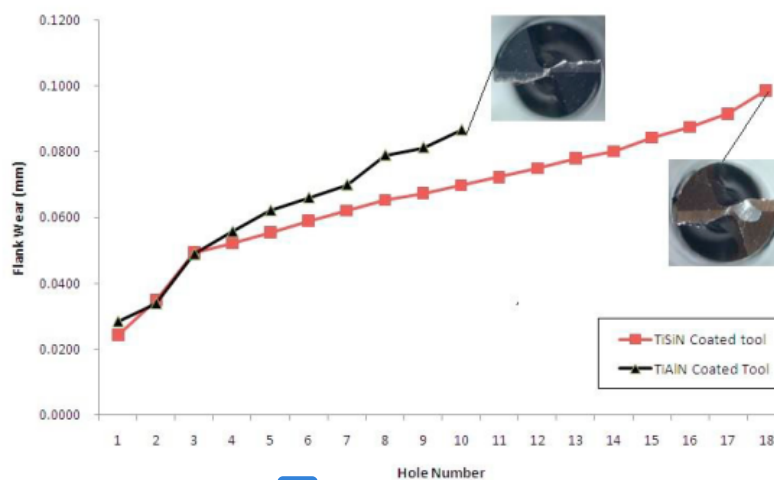


Fig. 2. Tool wear progression of TiSiN and TiAlN coated tools with the number of holes drilled.

The same analysis and similar hypothesis were applied for surface roughness response. ANOVA with two factors with replication is in Table 4.

Table 4. ANOVA result for surface roughness data.

Source of variation	Sum of square	Degree of freedom	Mean square	F	P-value	F <sub>critical</sub>	
Tool coating	0.433	1	0.433	5.29	0.05	5.32	Not significant
Tool condition	2.448	1	2.448	29.90	< 0.01	5.32	Significant
Interaction	0.071	1	0.071	0.86	0.38	5.32	Not significant
Within	0.655	8	0.082				
Total	3.607	11					

In terms of tool condition, since  $F(29.90) > F_{critical}(5.32)$ ,  $H_0$  was rejected and this means that surface roughness values for different tool conditions are statistically different. In other words, new and worn tools gave significantly different surface roughness. Related to tool coating, since  $F(5.29) < F_{critical}(5.32)$ ,  $H_0$  cannot be rejected and this means TiAlN coated and TiSiN coated tools gave no significant difference on surface roughness. Interaction between tool condition and tool coating on surface roughness not found to be significant since  $F(0.86) < F_{critical}(5.32)$  where  $H_0$  accepted.

Fig. 3 displays the surface roughness with increasing number of drilled holes under MQL-RPO drilling using different tool coating. The surface roughness for TiAlN coated tool was lower than TiSiN coated tool, and it decreases

with drilling distance. The lower surface roughness probably can be addressed to the smaller friction coefficient of TiAlN coating (0.55) than the TiSiN coating (0.9) on the tools as coefficient of friction directly determines the force required to produce movement [26]. Also, higher cutting force tends to trigger higher vibration. There is also possibility on the formation of the thin oxide layer of  $Al_2O_3$  as a result of the reaction between the TiAlN and the oxygen at the cutting zone for TiAlN coated tool [27]. The oxide layer acts as a solid lubrication thus reduces the friction and hence lowers the surface roughness.

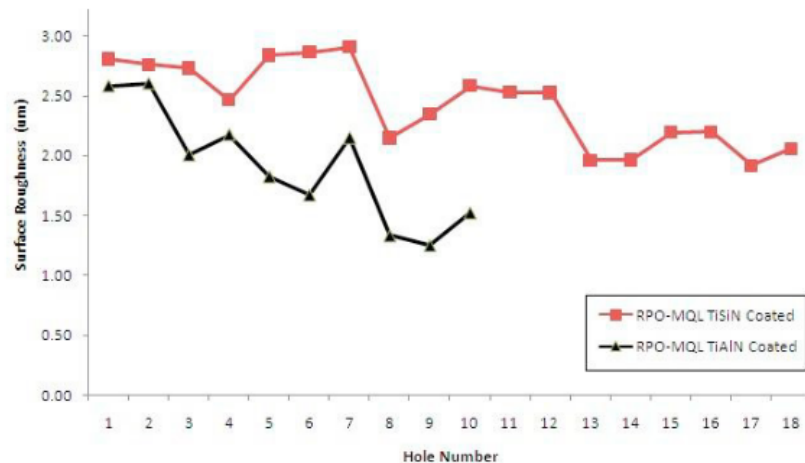


Fig. 3. Surface roughness (Ra) progression of TiSiN and TiAlN coated tools with the number of holes drilled.

### 3.3. Microstructure alterations

Fig. 4 shows the subsurface microstructures of the hole surface when drilling with different cooling condition. It was observed that a thin layer of plastic flow and microstructure deformation occurred towards the drilling direction. This deformed layer is due to the presence of high dislocation density. The transition in microstructure is probably due to high pressure of mechanical forces acting on the cutting tool during the drilling process on the workpiece [28]. In addition, deformation can occur due to high cutting temperatures that accompanies plastic deformation which produces a soft region (by thermal softening) underneath the machined surface.

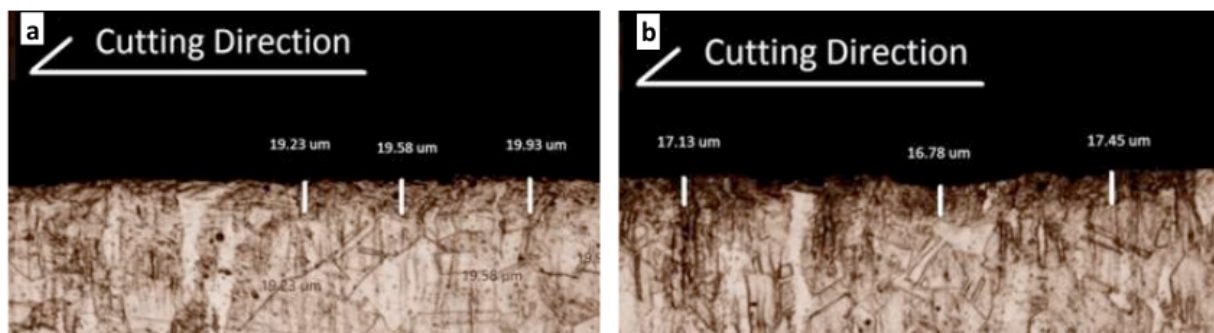


Fig. 4. Microstructures of the hole surface of the first hole when drilling using MQL-RPO (a) TiSiN coated carbide; (b) TiAlN coated carbide.

With regards to MQL-RPO drilling, using the same cutting condition under TiAlN coated carbide, the depth of affected layer and grain refinement on the surface and subsurface of drilled hole sample was found to be 17  $\mu m$  on average. When using TiSiN coated carbide, average subsurface deformation depth was found to be 19  $\mu m$ , which is

slightly deeper than for TiAlN coated carbide. TiAlN coated carbide produced less plastic deformation compared to TiSiN, probably due to formation of the thin oxide layer of  $Al_2O_3$  as a result of the reaction between the TiAlN and the oxygen. The oxide layer acts as a solid lubrication thus also reduces the friction during cutting and hence reducing workpiece temperature. As deformation temperature is lower, the mechanical loading could only penetrate to lower depth. This phenomenon is confirmed by the microstructure images (Fig. 4) and measured microhardness (Fig. 5) that show good agreement.

### 3.4. Microhardness variations

Fig. 5 shows the microhardness distribution beneath the surface at different coolant conditions. In general, similar trend is observed that the subsurface close to the machined surface shows high values of microhardness and these values decrease with depth until they stabilise and reach the hardness value of the bulk material. The highest hardness value at outer surface of the drilled hole was 250 HV for TiSiN while for TiAlN it was 210 HV.

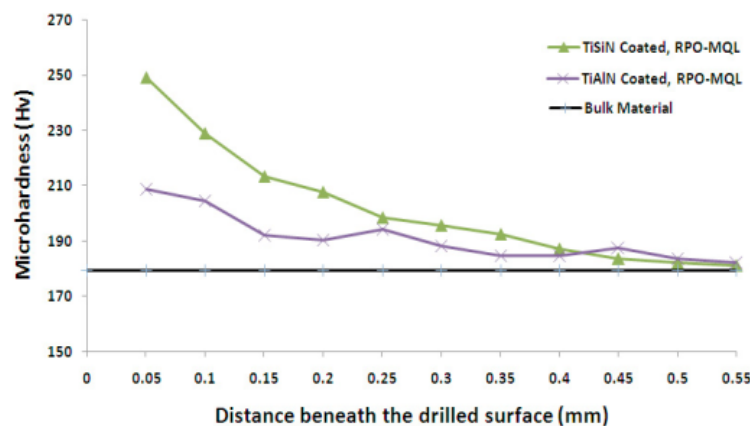


Fig. 5. Variation in microhardness value for different tool coatings.

Compared to the bulk material, the machined surface showed higher microhardness because of formation induced by mechanical loading of the drilling operations and might also be associated with localised high cutting temperature due to low thermal conductivity of the austenitic stainless steel. Similar result has been reported in our previous work [29] and by Liu et al [30] when they performed drilling of Nitinol.

## 4. Conclusions

The effect of using TiAlN and TiSiN coated carbide drill bits as cutting tools during minimum quantity of lubricant (MQL) drilling of austenitic stainless steel using refined palm olein (RPO) as lubricant/cutting fluid was evaluated. Based on statistical analysis (ANOVA), it was concluded that different tool coating has no significant effect on tool wear and surface roughness. It was also concluded that tool condition (new or worn tool) affects the surface roughness of the machined surface.

## Acknowledgement

Financial support from the Ministry of Higher Education, Malaysia and Universiti Teknologi Malaysia through Research University Grant scheme (no. 06H89) is gratefully acknowledged.



## References

- [1] U. S. Dixit, D. K. Sarma, J. P. Davim, Machining with minimal cutting fluid, in *Environmentally Friendly Machining*, Boston, USA: Springer (2012) 9-17.
- [2] N. Boubekri, V. Shaikh, P.R. Foster, A technology enabler for green machining: Minimum quantity lubrication (MQL), *Journal of Manufacturing Technology Management*, 21 (2010) 556-566.
- [3] N. J. Fox, G.W. Stachowiak, Vegetable oil-based lubricants—A review of oxidation, *Tribology International*, 40 (2007) 1035-1046.
- [4] W. Belluco, L. De Chiffre, Performance evaluation of vegetable-based oils in drilling austenitic stainless steel, *Journal of Materials Processing Technology*, 148 (2004) 171-176.
- [5] M. A. Xavier, M. Adithan, Determining the influence of cutting fluids on tool wear and surface roughness during turning of AISI 304 austenitic stainless steel, *Journal of Materials Processing Technology*, 209 (2009) 900-909.
- [6] B. Ozcelik, E. Kuram, M. H. Cetin, E. Demirbas, Experimental investigations of vegetable based cutting fluids with extreme pressure during turning of AISI 304L, *Tribology International*, 44 (2011) 1864-1871.
- [7] A. Z. Sultan, S. Sharif, D. Kurniawan, Examining the effect of various vegetable oil-based cutting fluids on surface integrity in drilling steel - A review, *Advanced Materials Research*, 845 (2014) 809-813.
- [8] E. Kuram, B. Ozcelik, E. Demirbas, E. Şik, I. N. Tansel, Evaluation of new vegetable-based cutting fluids on thrust force and surface roughness in drilling of AISI 304 using taguchi method, *Materials and Manufacturing Processes*, 26 (2011) 1136-1146.
- [9] M. H. S. Elmunafi, D. Kurniawan, M. Y. Noordin, Use of castor oil as cutting fluid in machining of hardened stainless steel with minimum quantity of lubricant, *Procedia CIRP*, 26 (2015) 408-411.
- [10] R. Heinemann, S. Hinduja, G. Barrow, G. Petuelli, Effect of MQL on the tool life of small twist drills in deep-hole drilling, *International Journal of Machine Tools and Manufacture*, 46 (2006) 1-6.
- [11] E. A. Rahim, H. Sasahara, Effect of MQL liquids on surface integrity when high speed drilling titanium alloy, *Key Engineering Materials*, 443 (2010) 359-364.
- [12] A. Filipovic, D. A. Stephenson, Minimum quantity lubrication (MQL) application in automotive power-train machining, *Machining Science and Technology*, 10 (2006) 3-22.
- [13] S. Sharif, M. A. Hisyam, S. Aman, Evaluation of vegetable oil as an alternative cutting lubricant when end milling martensitic stainless steel using uncoated carbide tool, *Journal of Advanced Manufacturing and Technology*, 3 (2009) 49-55.
- [14] W. J. Zheng, H. J. Pei, G. C. Wang, C. G. Shen, Effect of flow field on cutting fluid penetration during minimum quantity lubrication (MQL) machining, *Advanced Materials Research*, 188 (2011) 61-66.
- [15] L. C. Brandao, F. O. Neves, G. C. Nocelli, Evaluation of hole quality in hardened steel with high-speed drilling using different cooling systems, *Advances in Mechanical Engineering*, 3 (2011) 746535.
- [16] E. Kuram, E., B. Ozcelik, E. Demirbas, Environmentally friendly machining: Vegetable based cutting fluids, In: J. P. Davim, editor, *Green Manufacturing Processes and Systems, Materials Forming, Machining and Tribology*, Berlin: Springer, (2013) 23-47.
- [17] B. Ozcelik, E. Kuram, E. Demirbas, E. Şik, Optimization of surface roughness in drilling using vegetable-based cutting oils developed from sunflower oil, *Industrial Lubrication and Tribology*, 63 (2011) 271-276.
- [18] B. Ozcelik, E. Kuram, E. Demirbas, E. Şik, Effects of vegetable-based cutting fluids on the wear in drilling, *Sadhana - Academy Proceedings in Engineering Sciences*, 38 (2013) 687-706.
- [19] A. Shokrani, V. Dhokia, S. T. Newman, Environmentally conscious machining of difficult-to-machine materials with regard to cutting fluids, *International Journal of Machine Tools and Manufacture*, 57 (2012) 83-101.
- [20] S. Dolinšek, Work hardening in the drilling of austenitic stainless steels, *Journal of Materials Processing Technology*, 133 (2003) 63-70.
- [21] E. M. Trent, P.K. Wright, *Metal Cutting 4th ed*, Woburn, USA: Butterworth-Heinemann, (2000).
- [22] W. Li, P. J. Withers, D. Axinte, M. Preuss, P. Andrews, Residual stresses in face finish turning of high strength nickel-based superalloy, *Journal of Materials Processing Technology*, 209 (2009) 4896-4902.
- [23] U. Çaydaş, A. Haşçalık, Ö. Buytoz, A. Meyveci, Performance evaluation of different twist drills in dry drilling of AISI 304 austenitic stainless steel, *Materials and Manufacturing Processes*, 26 (2011) 951-960.
- [24] D. Petković, M. Madić, M. Radovanović, V. Gečevska, Application of the Performance Selection Index Method for Solving Machining MCDM Problems, *Facta Universitatis Series: Mechanical Engineering*, 15 (2017) 97-106.
- [25] C. Y. Wang, Y. X. Xie, Z. Qin, H. S. Lin, Y. H. Yuan, Q. M. Wang, Wear and breakage of TiAlN- and TiSiN-coated carbide tools during high-speed milling of hardened steel, *Wear*, 336 (2015) 29-42.
- [26] M. R. Stoudt, J. B. Hubbard, S. P. Mates, D. E. Green, Evaluating the relationships between surface roughness and friction behavior during metal forming, *SAE Technical Paper*, (2005) 2005-01-0500.
- [27] T. Cselle, A. Barimani, Today's applications and future developments of coatings for drills and rotating cutting tools, *Surface and Coatings Technology*, 76–77 (1995) 712-718.
- [28] M. M. Reddy, M. Kumar, K. Shanmugam, Finite element analysis and modeling of temperature distribution in turning of titanium alloys, *Metallurgical and Materials Engineering*, 24 (2018) 59-69.
- [29] A. Z. Sultan, S. Sharif, D. Kurniawan, Effect of machining parameters on tool wear and hole quality of AISI 316L stainless steel in conventional drilling, *Procedia Manufacturing*, 2 (2015) 202-207.
- [30] J. F. Liu, L. Li, Y. B. Guo, Surface integrity evolution from main cut to finish trim cut in w-edm of shape memory alloy, *Procedia CIRP*, 13 (2014) 137-142.

# Minimum quantity of lubricant drilling of stainless steel using refined palm olein: effect of coating tools on surface roughness and tool wear

---

ORIGINALITY REPORT

---

24%

SIMILARITY INDEX

---

PRIMARY SOURCES

---

- 1** Zul Fahmi Omar, Denni Kurniawan. "Effect of water treatment on AISI 316L stainless steel biocorrosion resistance", AIP Publishing, 2020 37 words — 1%  
Crossref
- 2** M.M. Ratnam. "1.1 Factors Affecting Surface Roughness in Finish Turning", Elsevier BV, 2017 36 words — 1%  
Crossref
- 3** Swain, Niharika, Vijay Venkatesh, Praveen Kumar, G. Srinivas, S. Ravishankar, and Harish C. Barshilia. "An experimental investigation on the machining characteristics of Nimonic 75 using uncoated and TiAlN coated tungsten carbide micro-end mills", CIRP Journal of Manufacturing Science and Technology, 2016. 35 words — 1%  
Crossref
- 4** K. Manoj Kumar, Nithin Tom Mathew, M. Baburaj. "Sustainable milling of Ti-6Al-4V super alloy using AlCrN and TiAlN coated tools", Materials Today: Proceedings, 2022 30 words — 1%  
Crossref
- 5** Grinspan, A.S.. "A novel surface modification technique for the introduction of compressive residual stress and preliminary studies on Al alloy AA6063", Surface & Coatings Technology, 20061005 25 words — 1%  
Crossref

6 Necati Uçak, Adem Çiçek. "The effects of cutting conditions on cutting temperature and hole quality in drilling of Inconel 718 using solid carbide drills", Journal of Manufacturing Processes, 2018

25 words — 1%

Crossref

7 Nwoguh, Theodore Obumselu. "Sustainable Face Milling of Inconel 718 Using MQL and Nanofluids MQL with Vegetable Oil as Base Fluid", Missouri University of Science and Technology, 2023

24 words — 1%

ProQuest

8 S. Ravi, P. Gurusamy. "Cryogenic machining of AISI p20 steel under liquid nitrogen cooling", Materials Today: Proceedings, 2021

24 words — 1%

Crossref

9 S Dolinšek. "Work-hardening in the drilling of austenitic stainless steels", Journal of Materials Processing Technology, 2003

23 words — 1%

Crossref

10 Inês S. Afonso, Glauco Nobrega, Rui Lima, José R. Gomes, João E. Ribeiro. "Conventional and Recent Advances of Vegetable Oils as Metalworking Fluids (MWFs): A Review", Lubricants, 2023

20 words — 1%

Crossref

11 Shaikh, Vasim. "Mist and microstructure characterization in end milling AISI 1018 steel using microlubrication.", Proquest, 2014.

20 words — 1%

ProQuest

12 Wang, C.Y., Y.X. Xie, Z. Qin, H.S. Lin, Y.H. Yuan, and Q.M. Wang. "Wear and breakage of TiAlN- and TiSiN-coated carbide tools during high-speed milling of hardened steel", Wear, 2015.

19 words — 1%

Crossref

- 
- 13 Abhijith Kunneparambil Sukumaran, Ananthan D Thampi, E Sneha, Muhammed Arif, S Rani. "Effect of bovine serum albumin on the lubricant properties of rice bran oil: a biomimetic approach", *Sādhanā*, 2021  
Crossref 18 words — 1%
- 
- 14 Rahim, Erween Abdul, and Hiroyuki Sasahara. "Application of Minimum Quantity Lubrication when Drilling Nickel-Based Superalloy at High Cutting Speed", *Key Engineering Materials*, 2009.  
Crossref 18 words — 1%
- 
- 15 Mustafa Yazici, Onur Çomaklı, Tuba Yetim, Ali Fatih Yetim, Ayhan Çelik. "Investigation of mechanical, tribological and magnetic properties after plasma nitriding of AISI 316L stainless steel produced with different orientations angles by selective laser melting", *Surface and Coatings Technology*, 2023  
Crossref 17 words — < 1%
- 
- 16 Rachamalla, Vishnu V.. "A Model of Stabilizer Roll Bearing for a Continuous Hot-dip Galvanizing Line", West Virginia University, 2020  
ProQuest 17 words — < 1%
- 
- 17 Zheng, W.J., H.J. Pei, Gui Cheng Wang, and C.G. Shen. "Effect of Flow Field on Cutting Fluid Penetration during Minimum Quantity Lubrication (MQL) Machining", *Advanced Materials Research*, 2011.  
Crossref 15 words — < 1%
- 
- 18 doaj.org  
Internet 15 words — < 1%
- 
- 19 citeseerx.ist.psu.edu  
Internet 14 words — < 1%
- 
- 20 "Techno-Societal 2018", Springer Science and Business Media LLC, 2020  
Crossref 13 words — < 1%

- 
- 21 P. N. Jyothi, M. Susmitha, P. Sharan. "Performance evaluation of NEEM oil and HONGE Oil as cutting fluid in drilling operation of mild steel", IOP Conference Series: Materials Science and Engineering, 2017  
Crossref 13 words — < 1%
- 
- 22 Rajesh Kumar Bhushan. "Effect of machining parameters on surface roughness and tool wear for 7075 Al alloy SiC composite", International Journal of Advanced Manufacturing Technology, 02/01/2010  
Crossref 13 words — < 1%
- 
- 23 tudr.thapar.edu:8080  
Internet 13 words — < 1%
- 
- 24 Emel Kuram, Babur Ozcelik, Mahmut Bayramoglu, Erhan Demirbas, Bilgin Tolga Simsek. "Optimization of cutting fluids and cutting parameters during end milling by using D-optimal design of experiments", Journal of Cleaner Production, 2013  
Crossref 12 words — < 1%
- 
- 25 dspace.library.uvic.ca:8080  
Internet 12 words — < 1%
- 
- 26 www.iaeng.org  
Internet 12 words — < 1%
- 
- 27 openrepository.aut.ac.nz  
Internet 11 words — < 1%
- 
- 28 teknik.trunojoyo.ac.id  
Internet 11 words — < 1%
- 
- 29 "Emerging Trends in Mechanical Engineering", Springer Science and Business Media LLC, 2020  
Crossref 10 words — < 1%

30 A A Premnath, T Alwarsamy, K Sugapriya. "A comparative analysis of tool wear prediction using response surface methodology and artificial neural networks", Australian Journal of Mechanical Engineering, 2015  
Crossref 10 words — < 1%

31 E. Sneha, Amjesh Revikumar, Jaykumar Y. singh, Ananthan D. Thampi, S. Rani. "Viscosity prediction of Pongamia pinnata (Karanja) oil by molecular dynamics simulation using GAFF and OPLS force field", Journal of Molecular Graphics and Modelling, 2020  
Crossref 10 words — < 1%

32 Lincoln Cardoso Brandão, Frederico Ozanan Neves, Gregório Christo Nocelli. "Evaluation of Hole Quality in Hardened Steel with High-Speed Drilling Using Different Cooling Systems", Advances in Mechanical Engineering, 2015  
Crossref 10 words — < 1%

33 [d.lib.msu.edu](http://d.lib.msu.edu)  
Internet 10 words — < 1%

34 [nrl.northumbria.ac.uk](http://nrl.northumbria.ac.uk)  
Internet 10 words — < 1%

35 [opus.bath.ac.uk](http://opus.bath.ac.uk)  
Internet 10 words — < 1%

36 [www.jstage.jst.go.jp](http://www.jstage.jst.go.jp)  
Internet 10 words — < 1%

37 Loredana Pop. "Basestock Oils for Lubricants from Mixtures of Corn Oil and Synthetic Diesters", Journal of the American Oil Chemists Society, 01/2008  
Crossref 9 words — < 1%

---

38 S. Sharma. "Optimization of Machining Process Parameters for Surface Roughness of Al-Composites", Journal of The Institution of Engineers (India): Series C, 2013  
9 words — < 1%  
Crossref

---

39 Ulaş Çaydaş, Ahmet Haşçalık, Ömer Buytoz, Ahmet Meyveci. "Performance Evaluation of Different Twist Drills in Dry Drilling of AISI 304 Austenitic Stainless Steel", Materials and Manufacturing Processes, 2011  
9 words — < 1%  
Crossref

---

40 digital.utsa.edu  
Internet  
9 words — < 1%

---

41 dokumen.pub  
Internet  
9 words — < 1%

---

42 pseccommunity.org  
Internet  
9 words — < 1%

---

43 strathprints.strath.ac.uk  
Internet  
9 words — < 1%

---

44 www.iraj.in  
Internet  
9 words — < 1%

---

45 www.mechanics-industry.org  
Internet  
9 words — < 1%

---

46 Amitava Mandal, Amit Rai Dixit, S. Chattopadhyaya, A. Paramanik, Sergej Hloch, Grzegorz Królczyk. "Improvement of surface integrity of Nimonic C 263 super alloy produced by WEDM through various post-processing techniques", The International Journal of Advanced Manufacturing Technology, 2017  
8 words — < 1%  
Crossref

47 Bogdan Arsene, Catalin Gheorghe, Flavius Aurelian Sarbu, Magdalena Barbu, Lucian-Ionel Cioca, Gavrilă Calefariu. "MQL-Assisted Hard Turning of AISI D2 Steel with Corn Oil: Analysis of Surface Roughness, Tool Wear, and Manufacturing Costs", Metals, 2021  
Crossref 8 words — < 1%

48 Debnath, Sujan, Moola Mohan Reddy, and Qua Sok Yi. "Environmental friendly cutting fluids and cooling techniques in machining: a review", Journal of Cleaner Production, 2014.  
Crossref 8 words — < 1%

49 E. Kuram. "Evaluation of New Vegetable Based Cutting Fluids on Thrust Force and Surface Roughness in Drilling of AISI 304 Using Taguchi Method", Materials and Manufacturing Processes, 2011  
Crossref 8 words — < 1%

50 Feng Jiao, Yuanxiao Li, Ying Niu, Ziqiang Zhang, Wenbo Bie. "A review on the drilling of CFRP/Ti stacks: Machining characteristics, damage mechanisms and suppression strategy at stack interface", Composite Structures, 2022  
Crossref 8 words — < 1%

51 Martyna Wiciak-Pikula, Agata Felusiak, Pawel Twardowski. "Artificial Neural Network models for tool wear prediction during Aluminium Matrix Composite milling", 2020 IEEE 7th International Workshop on Metrology for AeroSpace (MetroAeroSpace), 2020  
Crossref 8 words — < 1%

52 Obikawa, T.. "Micro-liter lubrication machining of Inconel 718", International Journal of Machine Tools and Manufacture, 200812  
Crossref 8 words — < 1%

53 Sharma, V.S.. "Cooling techniques for improved productivity in turning", International Journal of 8 words — < 1%



- 
- 54 Shokrani, , V. Dhokia, S.T. Newman, and R. Imani-Asrai. "An Initial Study of the Effect of Using Liquid Nitrogen Coolant on the Surface Roughness of Inconel 718 Nickel-Based Alloy in CNC Milling", *Procedia CIRP*, 2012. 8 words — < 1%  
Crossref
- 
- 55 [businessdocbox.com](http://businessdocbox.com) 8 words — < 1%  
Internet
- 
- 56 [dro.deakin.edu.au](http://dro.deakin.edu.au) 8 words — < 1%  
Internet
- 
- 57 [ndl.ethernet.edu.et](http://ndl.ethernet.edu.et) 8 words — < 1%  
Internet
- 
- 58 [www.ias.ac.in](http://www.ias.ac.in) 8 words — < 1%  
Internet
- 
- 59 S.A. Lawal, I.A. Choudhury, Y. Nukman. "Application of vegetable oil-based metalworking fluids in machining ferrous metals—A review", *International Journal of Machine Tools and Manufacture*, 2012. 7 words — < 1%  
Crossref
- 
- 60 Dabade, U.A.. "Surface finish and integrity of machined surfaces on Al/SiCp composites", *Journal of Materials Processing Tech.*, 20071001. 6 words — < 1%  
Crossref
- 
- 61 M.L. Shreeshail, Amol C. Desai, I.G. Siddhalingeswar, Krishnaraja G. Kodancha. "A study on influence of vegetable oils in milling operation and it's role as lubricant", *Materials Today: Proceedings*, 2021. 6 words — < 1%  
Crossref

---

62 Sheth Pushpak Chandrakant, Bhaveshkumar K. Patel. "A Review on the Effect of Minimum Quantity Lubrication on Different Machining Parameters Emphasizing Vegetable Oil-Based Lubricants for Sustainable Manufacturing", Advanced Materials Research, 2023  
Crossref 6 words — < 1%

---

63 Vinay Varghese, D. Chakradhar, M.R. Ramesh. "Micro-mechanical characterization and wear performance of TiAlN/NbN PVD coated carbide inserts during End milling of AISI 304 Austenitic Stainless Steel", Materials Today: Proceedings, 2018  
Crossref 6 words — < 1%

---

64 Vishal Yashwant Bhise, Bhagwan F. Jogi. "Recent developments on sustainable lubricants by using vegetable oil based nanofluids in machining", Materials Today: Proceedings, 2022  
Crossref 6 words — < 1%

---

65 [irep.iium.edu.my](http://irep.iium.edu.my)  
Internet 6 words — < 1%

---

66 [uknowledge.uky.edu](http://uknowledge.uky.edu)  
Internet 6 words — < 1%

---

EXCLUDE QUOTES OFF  
EXCLUDE BIBLIOGRAPHY ON

EXCLUDE SOURCES OFF  
EXCLUDE MATCHES OFF